

PHY 712 Electrodynamics
9-9:50 AM MWF Olin 105

Plan for Lecture 35:
Special Topics in Electrodynamics:
Electromagnetic aspects of
superconductivity

04/16/2018 PHY 712 Spring 2018 -- Lecture 35 1


23	Fri: 03/16/2018	Chap. 9	Harmonic radiation	#15	03/21/2018
24	Mon: 03/19/2018	Chap. 9 & 10	Interference and Scattering	#16	03/23/2018
25	Wed: 03/21/2018	Chap. 11	Special relativity	#17	03/26/2018
26	Fri: 03/23/2018	Chap. 11	Special relativity	#18	03/28/2018
27	Mon: 03/26/2018	Chap. 11	Special relativity		
28	Wed: 03/28/2018	Chap. 14	Radiation from accelerated particles		
	Fri: 03/30/2018	No class	Good Friday		
29	Mon: 04/02/2018	Chap. 14	Synchrotron radiation	#19	04/06/2018
30	Wed: 04/04/2018	Chap. 14	Synchrotron radiation	#20	04/09/2018
31	Fri: 04/06/2018	Chap. 15	Radiation from collisions of charged particles		
32	Mon: 04/09/2018	Chap. 13	Cherenkov radiation		
33	Wed: 04/11/2018		Review		
34	Fri: 04/13/2018		Review		
35	Mon: 04/16/2018		Special topic: Superconductivity		
36	Wed: 04/18/2018		Special topic: Superconductivity		
37	Fri: 04/20/2018		Special topic: Topics in optics		
38	Mon: 04/23/2018				
39	Wed: 04/25/2018				
	Fri: 04/27/2018		Presentations I		
	Mon: 04/30/2018		Presentations II		
	Wed: 05/02/2018		Presentations III		

04/16/2018 PHY 712 Spring 2018 -- Lecture 35 2

Wake Forest College & Graduate School of Arts and Sciences

WFU Physics

WFU Physics | People | Events and News | Undergraduate | Graduate | Research | Resources



Events

PhD Defense: "First-Principles Simulations of Solid State Battery Materials" April 17, 2018, at 2 PM
 Jason Howell, PhD Candidate, Public Presentation in Olin 107 Tuesday, April 17, 2018, at 2:00 PM
 Natalia Holzwarth, PhD Advisor The defense will follow. **ABSTRACT** in this work materials with ...

Colloquium: "When Ossians Merge, What Happens to Their Supermassive Black Holes?" Apr. 18, 2018, at 4 PM
 Dr. Tamara Bogdanovic - Associate Professor in the Center for Relativistic Astrophysics, School of Physics, Georgia Tech Georgia P Williams, Jr. Lecture Hall, (Olin 101) Wednesday, April 18, 2018, at ...


04/16/2018 PHY 712 Spring 2018 -- Lecture 35 3

Special topic: Electromagnetic properties of superconductors

Ref: D. Teplitz, editor, Electromagnetism – paths to research, Plenum Press (1982); Chapter 1 written by Brian Schwartz and Sonia Frota-Pessoa

History:

- 1908 H. Kamerlingh Onnes successfully liquified He
- 1911 H. Kamerlingh Onnes discovered that Hg at 4.2 K has vanishing resistance
- 1957 Theory of superconductivity by Bardeen, Cooper, and Schrieffer



04/16/2018

PHY 712 Spring 2018 – Lecture 35

4

Some phenomenological theories < 1957

Drude model of conductivity in "normal" materials

$$m \frac{dv}{dt} = -eE - m \frac{v}{\tau}$$

$$v(t) = v_0 e^{-t/\tau} - \frac{eE\tau}{m}$$

$$J = -nev \quad \text{for } t \gg \tau \quad J = \frac{ne^2\tau}{m} E \equiv \sigma E$$

London model of conductivity in superconducting materials; $\tau \rightarrow \infty$

$$m \frac{dv}{dt} = -eE$$

$$\frac{dv}{dt} = -\frac{eE}{m} \quad \frac{dJ}{dt} = -ne \frac{dv}{dt} = \frac{ne^2 E}{m}$$

From Maxwell's equations:

$$\nabla \times \mathbf{B} = \frac{4\pi}{c} \mathbf{J} + \frac{1}{c} \frac{\partial \mathbf{E}}{\partial t}$$

$$\nabla \times \mathbf{E} = -\frac{1}{c} \frac{\partial \mathbf{B}}{\partial t}$$

Note: Equations are in cgs Gaussian units.

04/16/2018

PHY 712 Spring 2018 – Lecture 35

5

Fritz London

Poland



Born in 1900 in Breslau (today Wrocław in Poland), Fritz London studied philosophy before choosing science. After getting a PhD in Munich in 1921, he understood what bonds two hydrogen atoms in a H₂ molecule. This work he did with Walter Heitler in Zurich was the starting point for the understanding of chemical bonding. Then he joined Erwin Schrödinger in Berlin but had to leave in 1933 because of the rise of anti-Semitism in Nazi Germany. After a stay in Oxford where he worked on superconductivity with his brother Heinz, he sought refuge at the Institut Henri Poincaré (Paris) in 1936, thanks to a group of intellectuals linked to the Popular Front (Jacques Hadamard, Paul Langevin, Jean Perrin, Frédéric Joliot and Edmond Bauer).

It is at that time, in 1938, that he explained that the **superfluidity** in liquid helium was a manifestation of **Bose-Einstein condensation**, a purely quantum phenomenon that could be seen for the first time on a macroscopic scale. This work followed a series of articles about superconductivity that could finally be understood as a superfluidity of charged particles (**electron pairs** in the case of superconducting metals).

At the beginning of World War II (September 1939), he left France and joined Duke University (USA) where Paul Gross had offered him a professorship in the Chemistry Department and where he felt more comfortable with his wife, the painter Edith London. Einstein wanted the Nobel Prize to be awarded to Fritz London, but London died prematurely in 1954.

04/16/2018

PHY 712 Spring 2018 – Lecture 35

6

Some phenomenological theories < 1957

London model of conductivity in superconducting materials

$$\frac{d\mathbf{J}}{dt} = -ne \frac{d\mathbf{v}}{dt} = \frac{ne^2}{m} \mathbf{E}$$

From Maxwell's equations:

$$\nabla \times \mathbf{B} = \frac{4\pi}{c} \mathbf{J} + \frac{1}{c} \frac{\partial \mathbf{E}}{\partial t} \quad \nabla \times \mathbf{E} = -\frac{1}{c} \frac{\partial \mathbf{B}}{\partial t}$$

$$\nabla \times (\nabla \times \mathbf{B}) = -\nabla^2 \mathbf{B} = \frac{4\pi}{c} \nabla \times \mathbf{J} - \frac{1}{c^2} \frac{\partial^2 \mathbf{B}}{\partial t^2}$$

$$-\nabla^2 \frac{\partial \mathbf{B}}{\partial t} = \frac{4\pi}{c} \nabla \times \frac{\partial \mathbf{J}}{\partial t} - \frac{1}{c^2} \frac{\partial^3 \mathbf{B}}{\partial t^3}$$

$$-\nabla^2 \frac{\partial \mathbf{B}}{\partial t} = \frac{4\pi ne^2}{mc} \nabla \times \mathbf{E} - \frac{1}{c^2} \frac{\partial^3 \mathbf{B}}{\partial t^3}$$

$$-\nabla^2 \frac{\partial \mathbf{B}}{\partial t} = -\frac{4\pi ne^2}{mc^2} \frac{\partial \mathbf{B}}{\partial t} - \frac{1}{c^2} \frac{\partial^3 \mathbf{B}}{\partial t^3}$$

$$\frac{\partial}{\partial t} \left(\nabla^2 - \frac{1}{\lambda_L^2} - \frac{1}{c^2} \frac{\partial^2}{\partial t^2} \right) \mathbf{B} = 0 \quad \text{with } \lambda_L^2 \equiv \frac{mc^2}{4\pi ne^2}$$

04/16/2018 PHY 712 Spring 2018 -- Lecture 35 7

London model – continued

London model of conductivity in superconducting materials

$$\frac{d\mathbf{J}}{dt} = -ne \frac{d\mathbf{v}}{dt} = \frac{ne^2}{m} \mathbf{E}$$

$$\frac{\partial}{\partial t} \left(\nabla^2 - \frac{1}{\lambda_L^2} - \frac{1}{c^2} \frac{\partial^2}{\partial t^2} \right) \mathbf{B} = 0 \quad \text{with } \lambda_L^2 \equiv \frac{mc^2}{4\pi ne^2}$$

For slowly varying solution:

$$\frac{\partial}{\partial t} \left(\nabla^2 - \frac{1}{\lambda_L^2} \right) \mathbf{B} = 0 \quad \text{for } \frac{\partial \mathbf{B}}{\partial t} = \hat{z} \frac{\partial B_z(x,t)}{\partial t}$$

$$\Rightarrow \frac{\partial B_z(x,t)}{\partial t} = \frac{\partial B_z(0,t)}{\partial t} e^{-x/\lambda_L}$$

London leap: $B_z(x,t) = B_z(0,t) e^{-x/\lambda_L}$

Consistent results for current density:

$$\frac{4\pi}{c} \nabla \times \mathbf{J} = -\nabla^2 \mathbf{B} = -\frac{1}{\lambda_L^2} \mathbf{B} \quad \mathbf{J} = \hat{y} J_y(x) \Rightarrow J_y(x) = \lambda_L \frac{ne^2}{mc} B_z(0) e^{-x/\lambda_L}$$

04/16/2018 PHY 712 Spring 2018 -- Lecture 35 8

London model – continued


Penetration length for superconductor: $\lambda_L^2 \equiv \frac{mc^2}{4\pi ne^2}$ Typically, $\lambda_L \approx 10^{-7} m$

$$B_z(x,t) = B_z(0,t) e^{-x/\lambda_L}$$

Vector potential for $\mathbf{B} = \nabla \times \mathbf{A}$ and $\nabla \cdot \mathbf{A} = 0$: Note that: $\nabla \times \mathbf{B} = \frac{4\pi}{c} \mathbf{J}$

$$\mathbf{A} = \hat{y} A_y(x) \quad A_y(x) = -\lambda_L B_z(0) e^{-x/\lambda_L} \quad -\nabla^2 \mathbf{A} = \frac{4\pi}{c} \mathbf{J} \Rightarrow \nabla^2 \mathbf{A} + \frac{4\pi}{c} \mathbf{J} = 0$$

Recall form for current density: $J_y(x) = \lambda_L \frac{ne^2}{mc} B_z(0) e^{-x/\lambda_L}$
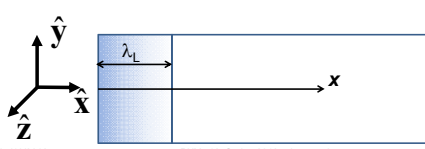
$$\Rightarrow \mathbf{J} + \frac{ne^2}{mc} \mathbf{A} = 0 \quad \text{or} \quad \frac{ne}{m} \left(m\mathbf{v} + \frac{e}{c} \mathbf{A} \right) = 0$$


04/16/2018 PHY 712 Spring 2018 -- Lecture 35 9

Behavior of superconducting material – exclusion of magnetic field according to the London model

Penetration length for superconductor: $\lambda_L^2 \equiv \frac{mc^2}{4\pi ne^2}$

$$B_z(x,t) = B_z(0,t)e^{-x/\lambda_L}$$


Vector potential for $\nabla \cdot \mathbf{A} = 0$:

$$\mathbf{A} = \hat{y}A_y(x) \quad A_y(x) = -\lambda_L B_z(0)e^{-x/\lambda_L}$$

$$\text{Current density: } J_y(x) = \lambda_L \frac{ne^2}{mc} B_z(0)e^{-x/\lambda_L}$$

$$\Rightarrow \mathbf{J} + \frac{ne^2}{mc} \mathbf{A} = 0 \quad \text{or} \quad \frac{ne}{m} \left(m\mathbf{v} + \frac{e}{c} \mathbf{A} \right) = 0$$

Typically, $\lambda_L \approx 10^{-7} m$



Behavior of magnetic field lines near superconductor


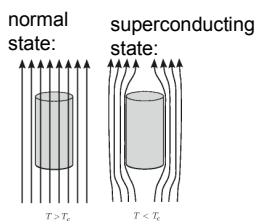


Figure 18.2 Exclusion of a weak external magnetic field from the interior of a superconductor.

The Meissner Effect

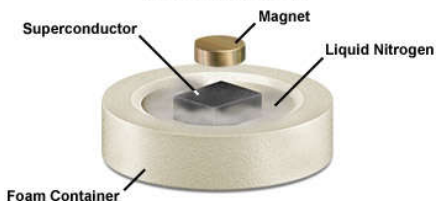

Need to consider phase equilibria between "normal" and superconducting state as a function of temperature and applied magnetic fields.

$$\mathbf{B} = \mathbf{H} + 4\pi\mathbf{M}$$

Within the superconductor, if $\mathbf{B} = 0$

$$\text{then } \mathbf{H} + 4\pi\mathbf{M} = 0 \quad \text{or } \mathbf{M} = -\frac{\mathbf{H}}{4\pi}$$

04/16/2018

PHY 712 Spring 2018 -- Lecture 35

13

Magnetization field

Treating London current in terms of corresponding magnetization field \mathbf{M} :

$$\mathbf{B} = \mathbf{H} + 4\pi\mathbf{M}$$

$$\Rightarrow \text{For } x \gg \lambda_L, \quad \mathbf{H} = -4\pi\mathbf{M}, \quad \mathbf{M}(\mathbf{H}) = -\frac{\mathbf{H}}{4\pi}$$

Gibbs free energy associated with magnetization for superconductor:

$$G_s(H_s) = G_s(H=0) - \int_0^{H_s} dHM(H) = G_s(0) - \int_0^{H_s} dH \left(\frac{-H}{4\pi} \right) = G_s(0) + \frac{1}{8\pi} H_s^2$$

This relation is true for an applied field $H_s \leq H_c$ when the superconducting and normal Gibbs free energies are equal:

$$G_s(H_c) = G_n(H_c) \approx G_n(H=0)$$

Condition at phase boundary between normal and superconducting states:

$$G_n(H_c) \approx G_n(0) = G_s(H_c) = G_s(0) + \frac{1}{8\pi} H_c^2 \quad \text{At } T=0K$$

$$\Rightarrow G_s(0) - G_n(0) = -\frac{1}{8\pi} H_c^2$$


$$G_s(H_s) - G_n(H_s) = \begin{cases} -\frac{1}{8\pi} (H_c^2 - H_s^2) & \text{for } H_s < H_c \\ 0 & \text{for } H_s > H_c \end{cases}$$

04/16/2018

PHY 712 Spring 2018 -- Lecture 35

14

Magnetization field (for "type I" superconductor)

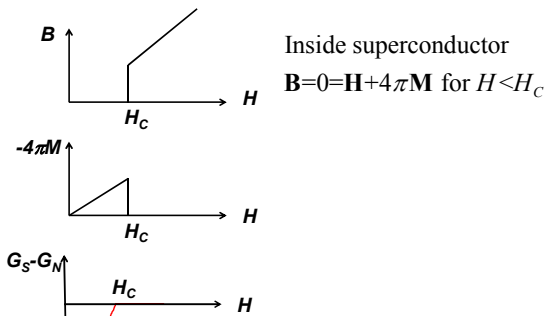

04/16/2018

PHY 712 Spring 2018 -- Lecture 35

15

PHYSICAL REVIEW VOLUME 108, NUMBER 5 DECEMBER 1, 1957

Theory of Superconductivity*

J. BARDEEN, L. N. COOPER,† and J. R. SCHRIEFER‡
Department of Physics, University of Illinois, Urbana, Illinois
 (Received July 8, 1957)

$$G_S(0) - G_N(0) = -\frac{H_c^2}{8\pi} \approx -2N(E_F)(\hbar\omega)^2 e^{-2/(N(E_F)V)}$$

characteristic phonon energy
 density of electron states at E_F
 attraction potential between electron pairs

04/16/2018 PHY 712 Spring 2018 - Lecture 35 16



Temperature dependence of critical field

$$H_c(T) \approx H_c(0) \left(1 - \left(\frac{T}{T_c} \right)^2 \right)$$

From PR 108, 1175 (1957) Bardeen, Cooper, and Schrieffer, "Theory of Superconductivity"

$$T_c \approx \frac{\hbar\omega}{k} e^{-2/(N(E_F)V)}$$

characteristic phonon energy
 density of electron states at E_F
 attraction potential between electron pairs

Fig. 2. Ratio of the critical field to its value at $T=0^\circ\text{K}$ as $(T/T_c)^2$. The upper curve is the $1 - (T/T_c)^2$ law of the Gorter-Casimir theory and the lower curve is the law predicted by the theory in the weak-coupling limit. Experimental values generally lie between the two curves.

04/16/2018 PHY 712 Spring 2018 - Lecture 35 17



Type I elemental superconductors

<http://wuphys.wustl.edu/~jss/NewPeriodicTable.pdf>

Periodic Table of Superconductivity

(dedicated to the memory of Bernd Matthias; compiled by James S. Schilling)

30 elements superconduct at ambient pressure, 25 more superconduct at high pressure.

ambient pressure superconductors										high pressure superconductors									
Li	Na	K	Rb	Cs	Ca	Y	Zr	Nb	Pb	Li	Na	K	Rb	Cs	Ca	Y	Zr	Nb	Pb
0.505 14	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10	0.39 10

M. Deleens, T. Matsumoto, J.J. Hamlin, W. Shi, Y. Meng, K. Shimizu, and J.S. Schilling, J Phys.: Conf. Series 215, 013034 (2010). High pressure data for Ca and Hb: K. Shimizu email from 9 Dec 2013.

04/16/2018 PHY 712 Spring 2018 - Lecture 35 18



Type I superconductors:

$$H_c(T) = H_c(0) \left(1 - \frac{T^2}{T_c^2}\right)$$

Figure 18.3 Schematic phase diagram illustrating normal and superconducting regions of a type-I superconductor.

Figure 18.4 Magnetization versus applied field for type-I superconductors.

04/16/2018 PHY 712 Spring 2018 – Lecture 35 19

Type II superconductors

Figure 18.5 Schematic phase diagram illustrating normal, mixed and Meissner regions of a type-II superconductor (the vanishingly small resistivity of the mixed state occurs if flux lines are "pinned" by appropriate material defects); in the mixed state, $\langle B \rangle$ denotes the average magnetic field in the superconductor.

Figure 18.6 Magnetization versus applied field H for a type-II superconductor. The equivalent area construction of the thermodynamic field $H_c(T)$ is also illustrated.

04/16/2018 PHY 712 Spring 2018 – Lecture 35 20

Quantization of current flux associated with the superconducting state (Ref: Ashcroft and Mermin, *Solid State Physics*)

From the London equations for the interior of the superconductor:

$$\left(m\mathbf{v} + \frac{e}{c}\mathbf{A}\right) = 0$$

Now suppose that the current carrier is a pair of electrons characterized by a wavefunction of the form $\psi = |\psi|e^{i\phi}$

The quantum mechanical current associated with the electron pair is

$$\mathbf{j} = -\frac{e\hbar}{2mi}(\psi^*\nabla\psi - \psi\nabla\psi^*) - \frac{2e^2}{mc}\mathbf{A}|\psi|^2$$

$$= -\left(\frac{e\hbar}{m}\nabla\phi + \frac{2e^2}{mc}\mathbf{A}\right)|\psi|^2$$

04/16/2018 PHY 712 Spring 2018 – Lecture 35 21

Quantization of current flux associated with the superconducting state -- continued



Suppose a superconducting material has a cylindrical void. Evaluate the integral of the current in a closed path within the superconductor containing the void.

$$\oint \mathbf{j} \cdot d\mathbf{l} = 0 = -\oint \left(\frac{e\hbar}{m} \nabla\phi + \frac{2e^2}{mc} \mathbf{A} \right) |\psi|^2 \cdot d\mathbf{l}$$

$$\oint \mathbf{A} \cdot d\mathbf{l} = \int (\nabla \times \mathbf{A}) \cdot d\mathbf{a} = \int \mathbf{B} \cdot d\mathbf{a} = \Phi \quad \text{magnetic flux}$$

$$\oint \nabla\phi \cdot d\mathbf{l} = 2\pi n \quad \text{for some integer } n$$

$$\Rightarrow \text{Quantization of flux in the void: } |\Phi| = n \frac{hc}{2e} \equiv n\Phi_0$$

Such "vortex" fields can exist within type II superconductors.

04/16/2018

PHY 712 Spring 2018 -- Lecture 35

22

Table 18.1 Critical temperature of some selected superconductors, and zero-temperature critical field. For elemental materials, the thermodynamic critical field $H_c(0)$ is given in gauss. For the compounds, which are type-II superconductors, the upper critical field $H_{c2}(0)$ is given in Tesla ($1 \text{ T} = 10^4 \text{ G}$). The data for metallic elements and binary compounds of V and Nb are taken from G. Burns (1992). The data for MgB_2 and iron pnictide are taken from the references cited in the text, and refer to the two principal crystallographic axes. The data for the other compounds are taken from D. R. Harshman and A. P. Mills, Phys. Rev. B 45, 10684 (1992). A more extensive list of data can be found in the mentioned references.

Material	T_c (K)	$H_c(0)$ (gauss)
Metallic elements		
Al	1.17	105
Sn	3.72	305
Pb	7.19	803
Hg	4.15	411
Nb	9.25	2060
V	5.40	1410
Binary compounds		
	T_c (K)	$H_{c2}(0)$ (Tesla)
V_3Ga	16.5	27
V_3Si	17.1	25
Nb_3Al	20.3	34
Nb_3Ge	23.3	38
MgB_2	40	≈ 5 ; ≈ 20
Other compounds		
	T_c (K)	$H_{c2}(0)$ (Tesla)
UPt_3 (heavy fermion)	0.53	2.1
PbMo_6S_8 (Chevrel phase)	12	55
κ - $(\text{BEDT-TTF})_x\text{Cu}(\text{NCS})_2$ (organic phase)	10.5	≈ 10
Rb_2C_{60} (fullerene)	31.3	≈ 30
$\text{NiFeAsO}_{0.7}\text{F}_{0.3}$ (iron pnictide)	47	≈ 30 ; ≈ 50
Cuprate oxides		
	T_c (K)	$H_{c2}(0)$ (Tesla)
$\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ ($x \approx 0.15$)	38	≈ 45
$\text{YBa}_2\text{Cu}_3\text{O}_7$	92	≈ 140
$\text{Bi}_2\text{Sr}_2\text{CaCu}_3\text{O}_{10}$	89	≈ 107
$\text{Tl}_2\text{Ba}_2\text{Ca}_2\text{Cu}_3\text{O}_{10}$	125	≈ 75

04/16/2018

PHY 712 Spring 2018 -- Lecture 35

23

Crystal structure of one of the high temperature superconductors




Figure 18.1 Crystal structure of the ceramic material La_2CuO_4 . Appropriately doped, lanthanum-based cuprates opened the path to high- T_c superconductivity in 1986.

04/16/2018

PHY 712 Spring 2018 -- Lecture 35

24

Some details of single vortex in type II superconductor

London equation without vortices:

$$\frac{4\pi}{c} \nabla \times \mathbf{J} = -\nabla^2 \mathbf{B} = -\frac{1}{\lambda_L^2} \mathbf{B} \quad \text{where } \lambda_L^2 \equiv \frac{mc^2}{4\pi ne^2}$$

Equation for field with single quantum of vortex along z - axis:

$$\nabla^2 \mathbf{B} - \frac{1}{\lambda_L^2} \mathbf{B} = -\frac{\Phi_0}{\lambda_L^2} \hat{z} \delta(\mathbf{r}) \quad \Phi_0 = \frac{hc}{2e} \quad \mathbf{r} = x\hat{x} + y\hat{y}$$

Solution: $\mathbf{B}(\mathbf{r}) = \hat{z} \frac{\Phi_0}{2\pi\lambda_L^2} K_0\left(\frac{r}{\lambda_L}\right)$

Check:

For $r > 0$ $\left(\frac{d^2}{dr^2} + \frac{1}{r} \frac{d}{dr} - \frac{1}{\lambda_L^2}\right) K_0\left(\frac{r}{\lambda_L}\right) = 0$

For $r \rightarrow 0$ $2\pi \int_0^r dr' r' \left(\frac{d^2}{dr'^2} + \frac{1}{r'} \frac{d}{dr'} - \frac{1}{\lambda_L^2}\right) K_0\left(\frac{r'}{\lambda_L}\right) = -2\pi$


Since $K_0(u) \approx -\ln u$ as $u \rightarrow 0$

04/16/2018


PHY 712 Spring 2018 -- Lecture 35

25

$$\mathbf{B}(\mathbf{r}) = \hat{z} \frac{\Phi_0}{2\pi\lambda_L^2} K_0\left(\frac{r}{\lambda_L}\right)$$



Scanning probe images of vortices in YBCO at 22 K



NSF EPSCoR
NSF Phys. 15-20493 (DORR) (NSF)

NSF DMR-15-07333 (NSF)

Fundamental studies of superconductors using scanning magnetic imaging

J R Kirtley

04/16/2018

PHY 712, Spring 2018 -- Lecture 35

26
