

## PHY 742 Quantum Mechanics II

1-1:50 AM MWF via video link:

<https://wakeforest-university.zoom.us/my/natalie.holzwarth>

### Plan for Lecture 34

A short introduction to the quantum theory of superconductivity

Bardeen, Cooper, Schrieffer, Phys. Rev. 108, 1175 (1957)

1. Cooper pairs
2. Gap equation
3. Estimate of  $T_c$

Some of the slides contain materials from the textbook, **Solid State Physics; Second Edition by Giuseppe Grosso and Giuseppe Pastori Parravicini (Academic Press, 2014)**

04/24/2020

PHY 742 -- Spring 2020 -- Lecture 34

1

We will go over some of the concepts of this famous paper.

21	Mon: 03/23/2020	Chap. 17	Quantization of the Electromagnetic Field	<a href="#">#17</a>	03/25/2020
22	Wed: 03/25/2020	Chap. 17	Quantization of the Electromagnetic Field	<a href="#">#18</a>	03/27/2020
23	Fri: 03/27/2020	Chap. 17	Quantization of the Electromagnetic Field	<a href="#">#19</a>	03/30/2020
24	Mon: 03/30/2020	Chap. 18	Photons and atoms		
25	Wed: 04/01/2020	Chap. 10	Multiparticle systems	<a href="#">#20</a>	04/03/2020
26	Fri: 04/03/2020	Chap. 10	Multiparticle systems	<a href="#">#21</a>	04/06/2020
27	Mon: 04/06/2020	Chap. 10	Multielectron atoms	<a href="#">#22</a>	04/08/2020
28	Wed: 04/08/2020	Chap. 10	Multielectron atoms		
	Fri: 04/10/2020	No class	<i>Good Friday</i>		
29	Mon: 04/13/2020	Chap. 10	Multielectron atoms	<a href="#">#23</a>	04/15/2020
30	Wed: 04/15/2020		Hartree-Fock and other formalisms	<a href="#">#24</a>	04/17/2020
31	Fri: 04/17/2020		Density functional theory		
32	Mon: 04/20/2020		Density functional theory for atoms		
33	Wed: 04/22/2020		Practical density functional theory		
34	Fri: 04/24/2020		Brief discussion of BCS theory of superconductivity		
35	Mon: 04/27/2020		Review		
36	Wed: 04/29/2020		Review		

Ongoing schedule

**Theory of Superconductivity\***

J. BARDEEN, L. N. COOPER,<sup>†</sup> AND J. R. SCHRIEFFER<sup>‡</sup>  
*Department of Physics, University of Illinois, Urbana, Illinois*  
(Received July 8, 1957)

A theory of superconductivity is presented, based on the fact that the interaction between electrons resulting from virtual exchange of phonons is attractive when the energy difference between the electrons states involved is less than the phonon energy,  $\hbar\omega$ . It is favorable to form a superconducting phase when this attractive interaction dominates the repulsive screened Coulomb interaction. The normal phase is described by the Bloch individual-particle model. The ground state of a superconductor, formed from a linear combination of normal state configurations in which electrons are virtually excited in pairs of opposite spin and momentum, is lower in energy than the normal state by amount proportional to an average  $(\hbar\omega)^2$ , consistent with the isotope effect. A mutually orthogonal set of excited states in

one-to-one correspondence with those of the normal phase is obtained by specifying occupation of certain Bloch states and by using the rest to form a linear combination of virtual pair configurations. The theory yields a second-order phase transition and a Meissner effect in the form suggested by Pippard. Calculated values of specific heats and penetration depths and their temperature variation are in good agreement with experiment. There is an energy gap for individual-particle excitations which decreases from about  $3.5kT_c$  at  $T=0^\circ\text{K}$  to zero at  $T_c$ . Tables of matrix elements of single-particle operators between the excited-state superconducting wave functions, useful for perturbation expansions and calculations of transition probabilities, are given.

## The Nobel Prize in Physics 1972



Photo from the Nobel Foundation archive.

**John Bardeen**

Prize share: 1/3



Photo from the Nobel Foundation archive.

**Leon Neil Cooper**

Prize share: 1/3

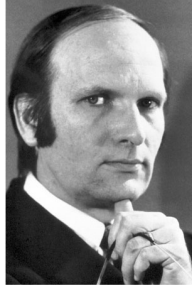


Photo from the Nobel Foundation archive.

**John Robert Schrieffer**

The Nobel Prize in Physics 1972 was awarded jointly to John Bardeen, Leon Neil Cooper and John Robert Schrieffer "for their jointly developed theory of superconductivity, usually called the BCS-theory."


Notion of a Cooper pair

Starting with a material with all the states filled up to the Fermi level, we focus attention on a pair of states which have a net attractive interaction  $U(\mathbf{r}_1, \mathbf{r}_2)$ :

$$\left[ \frac{\mathbf{p}_1^2}{2m} + \frac{\mathbf{p}_2^2}{2m} + U(\mathbf{r}_1, \mathbf{r}_2) \right] \psi(\mathbf{r}_1\sigma_1, \mathbf{r}_2\sigma_2) = E\psi(\mathbf{r}_1\sigma_1, \mathbf{r}_2\sigma_2)$$

$$\psi(\mathbf{r}_1\sigma_1, \mathbf{r}_2\sigma_2) = \phi(\mathbf{r}_1, \mathbf{r}_2)\chi(\sigma_1, \sigma_2)$$

**The thinking is that the interaction is related to lattice vibrations and had an energy  $\hbar\omega_D$**

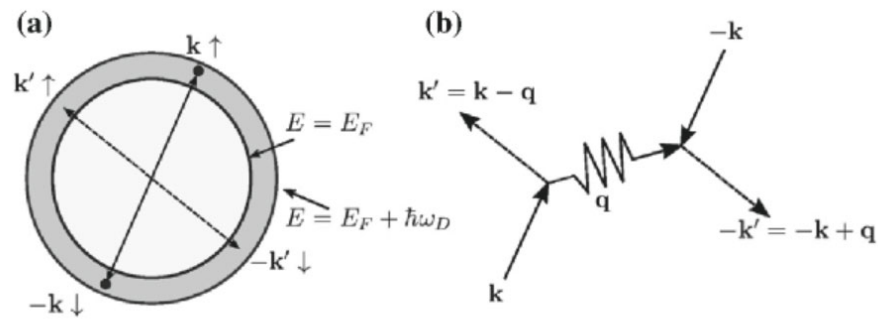

**Figure 18.7** (a) Schematic representation of a *single* Cooper pair, added to the ground state of a free-electron gas. Two “extra electrons” in the pair state  $(\mathbf{k}\uparrow, -\mathbf{k}\downarrow)$  scatter freely to the pair states  $(\mathbf{k}'\uparrow, -\mathbf{k}'\downarrow)$ , in the energy region  $E_F < E_{\mathbf{k}}, E_{\mathbf{k}'} < E_F + \hbar\omega_D$ , where the phonon-mediated attractive interaction is operative, and form a bound Cooper pair. (b) Schematic representation of the scattering of two electrons with wavevectors  $(\mathbf{k}, -\mathbf{k})$  into the state  $(\mathbf{k}', -\mathbf{k}')$  via the emission and subsequent absorption of a phonon of momentum  $\hbar\mathbf{q}$ .

Not sure that this helps... The thinking is that the pair of states are very close to the Fermi level.

Properties of pair wavefunction

$$\psi(\mathbf{r}_1\sigma_1, \mathbf{r}_2\sigma_2) = \phi(\mathbf{r}_1, \mathbf{r}_2)\chi(\sigma_1, \sigma_2)$$

Note:  $\sigma = \alpha \equiv \uparrow$

$\sigma = \beta \equiv \downarrow$

Spin part:

$$\chi^{(S=0)} = \frac{1}{\sqrt{2}}[\alpha(1)\beta(2) - \beta(1)\alpha(2)].$$

or

$$\chi^{(S=1)} = \begin{cases} \alpha(1)\alpha(2), \\ \frac{1}{\sqrt{2}}[\alpha(1)\beta(2) + \beta(1)\alpha(2)], \\ \beta(1)\beta(2), \end{cases}$$

Note that:

$$\chi^{S=0}(\sigma_1, \sigma_2) = -\chi^{S=0}(\sigma_2, \sigma_1)$$

$$\Rightarrow \phi^{S=0}(\mathbf{r}_1, \mathbf{r}_2) = \phi^{S=0}(\mathbf{r}_2, \mathbf{r}_1)$$

Note that:

$$\chi^{S=1}(\sigma_1, \sigma_2) = \chi^{S=1}(\sigma_2, \sigma_1)$$

$$\Rightarrow \phi^{S=1}(\mathbf{r}_1, \mathbf{r}_2) = -\phi^{S=1}(\mathbf{r}_2, \mathbf{r}_1)$$

The pair of electrons can have total spin 0 or 1 which determines the spatial symmetry to be symmetric or antisymmetric, respectively.

Properties of pair wavefunction – continued

Assume that the electron pair can be represented by a linear combination of plane wave states of wavevectors  $\mathbf{k}$  and  $-\mathbf{k}$ :

$$\phi(\mathbf{r}_1, \mathbf{r}_2) = \sum_{\mathbf{k}} g(\mathbf{k}) \frac{1}{V} e^{i\mathbf{k} \cdot (\mathbf{r}_1 - \mathbf{r}_2)}$$

Note that:

$$g^{S=0}(\mathbf{k}) = g^{S=0}(-\mathbf{k})$$

$$g^{S=1}(\mathbf{k}) = -g^{S=1}(-\mathbf{k})$$

Note that the states composing Cooper pairs are supposed to exist in the energy range  $E_F \leq E_{\mathbf{k}} \leq E_F + \hbar\omega_D$

It will be convenient to express the spatial part in terms of the Fourier representation.



Define Fourier transform of interaction potential:

$$\begin{aligned} U_{\mathbf{k}\mathbf{k}'} &= \iint \frac{1}{V} e^{-i\mathbf{k}\cdot(\mathbf{r}_1-\mathbf{r}_2)} U(\mathbf{r}_1-\mathbf{r}_2) \frac{1}{V} e^{i\mathbf{k}'\cdot(\mathbf{r}_1-\mathbf{r}_2)} d\mathbf{r}_1 d\mathbf{r}_2 \\ &= \frac{1}{N\Omega} \int e^{-i(\mathbf{k}-\mathbf{k}')\cdot\mathbf{r}} U(\mathbf{r}) d\mathbf{r} \end{aligned}$$

$V$  volume of sample composed of  $N$  unit cells

$\Omega$  volume of unit cell

Equation satisfied by pair amplitude functions:

$$(2E_{\mathbf{k}} - E)g(\mathbf{k}) + \sum_{\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} g(\mathbf{k}') = 0 \quad E_F < E_{\mathbf{k}}, E_{\mathbf{k}'} < E_F + \hbar\omega_D$$

Here is the equation that the unknown amplitude  $g(\mathbf{k})$  must satisfy. The initial states are below the Fermi level and scattered states are above the Fermi level.

Cooper pair equations -- continued

$$(2E_{\mathbf{k}} - E)g(\mathbf{k}) + \sum_{\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} g(\mathbf{k}') = 0 \quad E_F < E_{\mathbf{k}}, E_{\mathbf{k}'} < E_F + \hbar\omega_D$$

Simplified model for interaction:

$$U_{\mathbf{k}\mathbf{k}'} = -U_0/N$$

$$(2E_{\mathbf{k}} - E)g(\mathbf{k}) - U_0 \frac{1}{N} \sum_{\mathbf{k}'} g(\mathbf{k}') = 0 \quad E_F < E_{\mathbf{k}}, E_{\mathbf{k}'} < E_F + \hbar\omega_D; \quad U_0 > 0.$$

In this approximation, for triplet states  $\sum_{\mathbf{k}} g^{S=1}(\mathbf{k}) = 0$


$\Rightarrow$  Cooper pair states can only be singlet states

Simplifying the interaction term to a constant. Why must Cooper pair states have singlet spin?

Cooper pair equations -- continued

Non-trivial solution for singlet state:

$$(2E_{\mathbf{k}} - E)g(\mathbf{k}) - U_0 \frac{1}{N} \sum_{\mathbf{k}'} g(\mathbf{k}') = 0$$



Equation to determine eigenstate energy:

$$1 = U_0 \frac{1}{N} \sum_{\mathbf{k}} \frac{1}{2E_{\mathbf{k}} - E_{\text{pair}}} \quad E_F < E_{\mathbf{k}} < E_F + \hbar\omega_D.$$

$$1 = U_0 \frac{1}{N} \int_{E_F}^{E_F + \hbar\omega_D} D_0(E) \frac{1}{2E - E_{\text{pair}}} dE,$$



Density of states (one electron basis)

How does the derivation of the eigenstate energy equation work?

### Cooper pair equations -- continued

$$1 = U_0 n_0 \int_{E_F}^{E_F + \hbar\omega_D} \frac{1}{2E - E_{\text{pair}}} dE = \frac{1}{2} U_0 n_0 \ln \frac{2E_F + 2\hbar\omega_D - E_{\text{pair}}}{2E_F - E_{\text{pair}}}$$

where  $n_0 \equiv \frac{D_0(E_F)}{N} = \frac{3}{4} \frac{Z}{E_F}$  denoting Fermi level DOS for a single spin  
for simple metal of valence  $Z$

$$\Delta_b = 2E_F - E_{\text{pair}} = \hbar\omega_D \frac{e^{-1/U_0 n_0}}{\sinh[1/U_0 n_0]} \approx 2\hbar\omega_D \exp[-2/U_0 n_0].$$

**Shows that a singlet Cooper pair is more stable than the independent particle system even for small  $U_0$ .**

Why do we conclude that the Cooper pair is more stable?

## Variational determination of the ground-state wavefunction in the BCS model

### Second quantization

$$\{c_{\mathbf{k}\sigma}, c_{\mathbf{k}'\sigma'}\} = \{c_{\mathbf{k}\sigma}^\dagger, c_{\mathbf{k}'\sigma'}^\dagger\} = 0, \quad \{c_{\mathbf{k}\sigma}, c_{\mathbf{k}'\sigma'}^\dagger\} = \delta_{\mathbf{k}\mathbf{k}'}\delta_{\sigma\sigma'}.$$

Note that the Cooper pair singlet state can be written

$$\begin{aligned} \psi(\mathbf{r}_1\sigma_1, \mathbf{r}_2\sigma_2) &= \sum_{\mathbf{k}} g(\mathbf{k}) \frac{1}{\sqrt{2}} \frac{1}{V} \left[ e^{i\mathbf{k}\cdot(\mathbf{r}_1-\mathbf{r}_2)} \alpha(1)\beta(2) - e^{-i\mathbf{k}\cdot(\mathbf{r}_1-\mathbf{r}_2)} \beta(1)\alpha(2) \right] \\ &\equiv \sum_{\mathbf{k}} g(\mathbf{k}) c_{\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}\downarrow}^\dagger |0\rangle, \end{aligned}$$

It is convenient to use second quantization

**Variational determination of the ground-state wavefunction in the BCS model -- continued**

$$H = \underbrace{\sum_{\mathbf{k}} E_{\mathbf{k}} (c_{\mathbf{k}\uparrow}^{\dagger} c_{\mathbf{k}\uparrow} + c_{-\mathbf{k}\downarrow}^{\dagger} c_{-\mathbf{k}\downarrow})}_{\text{independent particle states}} + \underbrace{\sum_{\mathbf{k}\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} c_{\mathbf{k}\uparrow}^{\dagger} c_{-\mathbf{k}\downarrow}^{\dagger} c_{-\mathbf{k}'\downarrow} c_{\mathbf{k}'\uparrow}}_{\text{Cooper-pair interaction}}$$

Consider a ground state wavefunction of the form

$$|\Psi_S\rangle = \prod_{\mathbf{k}} (u_{\mathbf{k}} + v_{\mathbf{k}} c_{\mathbf{k}\uparrow}^{\dagger} c_{-\mathbf{k}\downarrow}^{\dagger}) |0\rangle,$$

$$u_{\mathbf{k}}^2 + v_{\mathbf{k}}^2 = 1$$

probability amplitude for forming Cooper pair

Hamiltonian of the BCS model. The parameters  $u$  and  $v$  will be determined variationally.

**Variational determination of the ground-state wavefunction in the BCS model -- continued**

**Need to minimize the expectation value:**

$$W_S = \langle \Psi_S | H_{\text{BCS}} | \Psi_S \rangle$$

$$H_{\text{BCS}} = \sum_{\mathbf{k}} \varepsilon_{\mathbf{k}} (c_{\mathbf{k}\uparrow}^\dagger c_{\mathbf{k}\uparrow} + c_{-\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}\uparrow}) + \sum_{\mathbf{k}\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} c_{\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}\downarrow}^\dagger c_{-\mathbf{k}'\downarrow} c_{\mathbf{k}'\uparrow}$$

$$\varepsilon_{\mathbf{k}} = E_{\mathbf{k}} - \mu = (\hbar^2 \mathbf{k}^2 / 2m) - \mu$$

**After some algebra:**

$$W_S = \langle \Psi_S | H_{\text{BCS}} | \Psi_S \rangle = 2 \sum_{\mathbf{k}} \varepsilon_{\mathbf{k}} v_{\mathbf{k}}^2 + \sum_{\mathbf{k}\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} u_{\mathbf{k}} v_{\mathbf{k}} u_{\mathbf{k}'} v_{\mathbf{k}'}$$

Writing out the energy to be determined variationally.

## Variational determination of the ground-state wavefunction in the BCS model -- continued

Convenient transformation:

$$\begin{cases} u_{\mathbf{k}} = \cos \theta_{\mathbf{k}} \\ v_{\mathbf{k}} = \sin \theta_{\mathbf{k}} \end{cases} \implies \sin 2\theta_{\mathbf{k}} = 2u_{\mathbf{k}}v_{\mathbf{k}}; \quad \cos 2\theta_{\mathbf{k}} = u_{\mathbf{k}}^2 - v_{\mathbf{k}}^2.$$

$$W_S = 2 \sum_{\mathbf{k}} \varepsilon_{\mathbf{k}} \sin^2 \theta_{\mathbf{k}} + \frac{1}{4} \sum_{\mathbf{k}\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} \sin 2\theta_{\mathbf{k}} \sin 2\theta_{\mathbf{k}'}$$

$$\frac{\partial W_S}{\partial \theta_{\mathbf{k}}} = 0 \implies 2\varepsilon_{\mathbf{k}} \sin 2\theta_{\mathbf{k}} + \sum_{\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} \cos 2\theta_{\mathbf{k}} \sin 2\theta_{\mathbf{k}'} = 0$$

$$\implies 2\varepsilon_{\mathbf{k}} u_{\mathbf{k}} v_{\mathbf{k}} + \sum_{\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} (u_{\mathbf{k}}^2 - v_{\mathbf{k}}^2) u_{\mathbf{k}'} v_{\mathbf{k}'} = 0$$

**Define:** 
$$\Delta_{\mathbf{k}} = - \sum_{\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} u_{\mathbf{k}'} v_{\mathbf{k}'}$$

04/24/2020

PHY 742 -- Spring 2020 -- Lecture 34

16

Clever tricks and notations.



**Variational determination of the ground-state wavefunction in the BCS model -- continued**

In terms of the “gap parameter” the variational equations become:

$$2\varepsilon_{\mathbf{k}}u_{\mathbf{k}}v_{\mathbf{k}} - \Delta_{\mathbf{k}}(u_{\mathbf{k}}^2 - v_{\mathbf{k}}^2) = 0.$$

$$u_{\mathbf{k}}^2 = \frac{1}{2} \left[ 1 + \frac{\varepsilon_{\mathbf{k}}}{\sqrt{\varepsilon_{\mathbf{k}}^2 + \Delta_{\mathbf{k}}^2}} \right] \quad \text{and} \quad v_{\mathbf{k}}^2 = \frac{1}{2} \left[ 1 - \frac{\varepsilon_{\mathbf{k}}}{\sqrt{\varepsilon_{\mathbf{k}}^2 + \Delta_{\mathbf{k}}^2}} \right].$$

$$\Delta_{\mathbf{k}} = -\frac{1}{2} \sum_{\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} \frac{\Delta_{\mathbf{k}'}}{\sqrt{\varepsilon_{\mathbf{k}'}^2 + \Delta_{\mathbf{k}'}^2}}$$

In the end, we have an integral equation for the gap parameter.

## Variational determination of the ground-state wavefunction in the BCS model -- continued

### Simplified model

$$U_{\mathbf{k}\mathbf{k}'} = \begin{cases} -U_0/N & \text{if } |\varepsilon_{\mathbf{k}}|, |\varepsilon_{\mathbf{k}'}| < \hbar\omega_D \quad (U_0 > 0), \\ 0 & \text{otherwise,} \end{cases}$$

$$\Delta_{\mathbf{k}} = \begin{cases} \Delta_0 & \text{if } |\varepsilon_{\mathbf{k}}| < \hbar\omega_D, \\ 0 & \text{otherwise.} \end{cases}$$

$$1 = \frac{1}{2} U_0 \frac{1}{N} \sum_{\mathbf{k}'} \frac{1}{\sqrt{\varepsilon_{\mathbf{k}'}^2 + \Delta_0^2}} \quad \text{with} \quad -\hbar\omega_D < \varepsilon_{\mathbf{k}'} < \hbar\omega_D.$$

Using DOS: 
$$1 = \frac{1}{2} U_0 n_0 \int_{-\hbar\omega_D}^{\hbar\omega_D} \frac{d\varepsilon}{\sqrt{\varepsilon^2 + \Delta_0^2}},$$

Make a simplified model for the interaction term in order to solve the equation.

**Variational determination of the ground-state wavefunction in the BCS model -- continued**

$$1 = \frac{1}{2} U_0 n_0 \int_{-\hbar\omega_D}^{\hbar\omega_D} \frac{d\varepsilon}{\sqrt{\varepsilon^2 + \Delta_0^2}} = U_0 n_0 \sinh^{-1} \frac{\hbar\omega_D}{\Delta_0}$$

**Solving for the gap parameter:**

$$\Delta_0 = \frac{\hbar\omega_D}{\sinh(1/U_0 n_0)} \approx 2\hbar\omega_D \exp[-1/U_0 n_0]$$

**Estimating the ground state energy of the superconducting state:**

$$W_S - W_N = 2 \sum_{\mathbf{k}} \varepsilon_{\mathbf{k}} v_{\mathbf{k}}^2 + \sum_{\mathbf{k}\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} u_{\mathbf{k}} v_{\mathbf{k}} u_{\mathbf{k}'} v_{\mathbf{k}'} - 2 \sum_{\mathbf{k}}^{k < k_F} \varepsilon_{\mathbf{k}}$$

## Estimating the ground state energy of the superconducting state – continued

Using the variational solution and integrating the DOS:

$$W_S - W_N = D_0(E_F) \int_{-\hbar\omega_D}^{\hbar\omega_D} \left( \varepsilon - \frac{2\varepsilon^2 + \Delta_0^2}{2\sqrt{\varepsilon^2 + \Delta_0^2}} \right) d\varepsilon - D_0(E_F) \int_{-\hbar\omega_D}^0 2\varepsilon d\varepsilon.$$

$$W_S - W_N = D_0(E_F) \left[ -\hbar\omega_D \sqrt{\hbar^2\omega_D^2 + \Delta_0^2} + \hbar^2\omega_D^2 \right].$$

$$\approx -\frac{1}{2} D_0(E_F) \Delta_0^2$$

Here we assume that the gap parameter is smaller than the phonon energy.

**Effects of temperature:**

**Thermal average of Cooper pair operator:**

$$a_{\mathbf{k}} = \langle c_{\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}\downarrow}^\dagger \rangle_T$$

**Define**

$$c_{\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}\downarrow}^\dagger = a_{\mathbf{k}} + (c_{\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}\downarrow}^\dagger - a_{\mathbf{k}}),$$

**average**

**fluctuations**

Now we need to consider how temperature affects the analysis.

### Modified Gap relationship

$$\Delta_{\mathbf{k}} = - \sum_{\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} u_{\mathbf{k}'} v_{\mathbf{k}'} [1 - 2f(w_{\mathbf{k}'})] \quad \text{with} \quad w_{\mathbf{k}} = \sqrt{\varepsilon_{\mathbf{k}}^2 + \Delta_{\mathbf{k}}^2}.$$

### Fermi-Dirac distribution

$$f(E) = \frac{1}{e^{\beta E} + 1} \implies 1 - 2f(E) = \tanh \frac{\beta E}{2},$$

### Modified Gap equation

$$\Delta_{\mathbf{k}} = -\frac{1}{2} \sum_{\mathbf{k}'} U_{\mathbf{k}\mathbf{k}'} \frac{\Delta_{\mathbf{k}'}}{\sqrt{\varepsilon_{\mathbf{k}'}^2 + \Delta_{\mathbf{k}'}^2}} \tanh \frac{\beta \sqrt{\varepsilon_{\mathbf{k}'}^2 + \Delta_{\mathbf{k}'}^2}}{2}.$$

Introducing the Fermi-Dirac distribution

### Simplified model

$$U_{\mathbf{k}\mathbf{k}'} = \begin{cases} -U_0/N & \text{if } |\varepsilon_{\mathbf{k}}|, |\varepsilon_{\mathbf{k}'}| < \hbar\omega_D \quad (U_0 > 0), \\ 0 & \text{otherwise,} \end{cases}$$

$$1 = \frac{1}{2} U_0 n_0 \int_{-\hbar\omega_D}^{\hbar\omega_D} \frac{d\varepsilon}{\sqrt{\varepsilon^2 + \Delta^2}} \tanh \frac{\beta\sqrt{\varepsilon^2 + \Delta^2}}{2}.$$

Determine the critical temperature such that  $\Delta(T_c) = 0$ :

$$1 = U_0 n_0 \int_0^{\hbar\omega_D} \frac{1}{\varepsilon} \tanh \frac{\varepsilon}{2k_B T_c} d\varepsilon,$$

Evaluating expressions for simplified model

### Evaluation of the integral

$$I(a) = \int_0^a \frac{1}{x} \tanh x \, dx = [\tanh x \ln x]_0^a - \int_0^a \ln x \frac{1}{\cosh^2 x} \, dx$$

(for  $a \gg 1$ )  $\approx \ln a - \int_0^\infty \ln x \frac{1}{\cosh^2 x} \, dx = \ln a + \ln \frac{4\gamma}{\pi}$   $\gamma = 1.78107 \dots$

If  $\frac{\hbar\omega_D}{2k_B T_c} \gg 1$ :

$$\int_0^{\hbar\omega_D/2k_B T_c} \frac{1}{x} \tanh x \, dx = \ln \left( \frac{2\gamma}{\pi} \frac{\hbar\omega_D}{k_B T_c} \right) \approx \ln \frac{1.13\hbar\omega_D}{k_B T_c} = \frac{1}{U_0 n_0}.$$

Then, in the weak coupling limit  $U_0 n_0 \ll 1$  and  $\hbar\omega_D/k_B T_c \gg 1$ , we have


$$k_B T_c = 1.13 \hbar\omega_D \exp[-1/U_0 n_0].$$

Some arithmetic...



Numerical evaluation of integral:

$$1 = \frac{1}{2} U_0 n_0 \int_{-\hbar\omega_D}^{\hbar\omega_D} \frac{d\varepsilon}{\sqrt{\varepsilon^2 + \Delta^2}} \tanh \frac{\beta\sqrt{\varepsilon^2 + \Delta^2}}{2},$$
$$1 = U_0 n_0 \int_0^{\hbar\omega_D} \frac{1}{\varepsilon} \tanh \frac{\varepsilon}{2k_B T_c} d\varepsilon,$$

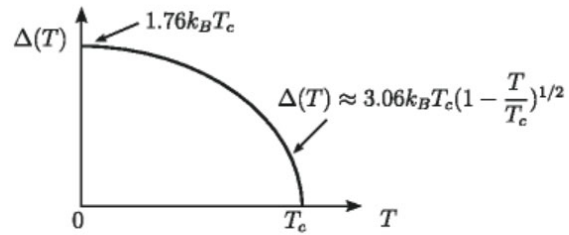

**Figure 18.12** Behavior of the energy gap parameter  $\Delta(T)$  for a superconductor in the BCS theory and in weak coupling limit.

At the critical temperature, the gap is 0. Graph shows qualitative temperature dependence.

### Estimation of critical magnetic field (BCS paper)

$$H_c^2/8\pi = F_n - F_s,$$



Free energy of  
normal state



Free energy of  
superconducting state

After some approximations, etc.:

$$\frac{H_c^2}{8\pi} = N(0)(\hbar\omega)^2 \left\{ \left[ 1 + \left( \frac{\epsilon_0}{\hbar\omega} \right)^2 \right]^{1/2} - 1 \right\} - \frac{\pi^2}{3} N(0)(kT)^2$$
$$\times \left\{ 1 - \beta^2 \int_0^\infty d\epsilon \left[ \frac{2\epsilon^2 + \epsilon_0^2}{E} \right] f(\beta E) \right\}. \quad (3.38)$$

Relationship to critical field.

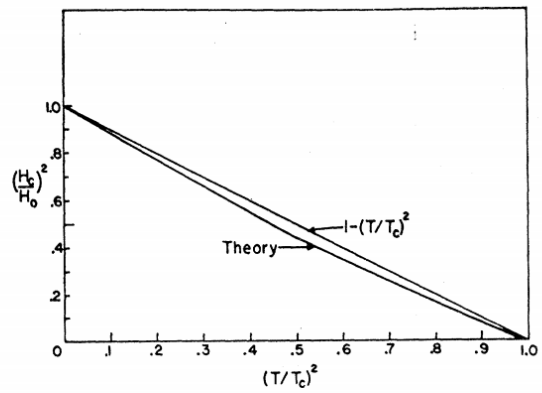


FIG. 2. Ratio of the critical field to its value at  $T=0^\circ\text{K}$  vs  $(T/T_c)^2$ . The upper curve is the  $1 - (T/T_c)^2$  law of the Gorter-Casimir theory and the lower curve is the law predicted by the theory in the weak-coupling limit. Experimental values generally lie between the two curves.

Figure from BCS theory showing agreement with experiment.